

REVIEW

Efficient Dye Removal Strategies: Exploring the Role of Biochar

Rupali Chavan¹, Rahul Patil^{**2}, and Ashok Chougale^{*1}

ABSTRACT: The surge in industrial activities, notably in sectors such as textiles, leather processing, and paper manufacturing, has led to a considerable rise in synthetic dye discharge into the environment, posing significant threats to ecosystems and human health. Traditional wastewater treatment methods have struggled to effectively address dye pollution due to the complex nature of these pollutants. In response, biochar has emerged as a promising solution, offering unique physicochemical properties that make it an excellent adsorbent for dye removal. This review explores the role of biochar in dye removal, focusing on its surface properties, production methods, and adsorption mechanisms. Biochar's extensive surface area, porosity, and surface functional groups play crucial roles in facilitating dye adsorption. Various production methods, such as pyrolysis, hydrothermal carbonization, and superheated steam torrefaction, influence biochar properties and effectiveness in dye removal applications. Surface modification techniques enhance biochar's dye removal capacity and regeneration potential, enabling its reuse in wastewater treatment. Moreover, the surface charge of biochar influences electrostatic interactions with dye molecules, affecting adsorption efficiency. Understanding biochar's surface charge is essential for optimizing dye removal processes. Overall, biochar holds promise as a sustainable and efficient adsorbent for mitigating dye pollution, offering valuable insights for environmental remediation efforts.

Keywords: Biochar; Dye removal; Surface properties; Adsorption mechanisms; Regeneration; Surface charge; Surface area

Received: 16 January 2024; Revised: 28 February 2024; Accepted: 17 March 2024; Published Online: 20 March 2024

1. INTRODUCTION

In recent years, industries such as textiles, leather processing, and paper manufacturing have experienced rapid expansion, leading to a significant increase in the discharge of synthetic dyes into the environment [1, 2]. This influx of dyes poses a serious threat to aquatic ecosystems and human health [3, 4]. Synthetic dyes are known for their persistence, toxicity, and non-biodegradability, making them particularly challenging to address once they enter water bodies. Traditional wastewater treatment methods, including chemical, physical, and biological approaches, have struggled to effectively treat dye-containing wastewater due to the complex nature of these pollutants. Currently, there is a surge of ongoing research directed towards the effective

removal of dyes from wastewater [5–7].

In response to the urgent need for sustainable and efficient methods to address dye pollution, biochar has emerged as a promising solution. Biochar is a carbonaceous material produced from the pyrolysis of organic biomass under oxygen-limited conditions. This process results in the production of solid (biochar), liquid (oil), and gaseous products. Biochar is a valuable material that can be utilized as a soil additive for nutrient improvement and carbon sequestration, where the carbon can be stored (locked) in the soil, improving soil structure, pH, water and nutrient retention, and mitigating climate change [8]. It can also be used as a biofuel in energy generation directly or converted to biomass briquettes, enhancing its energy and economic value [8]. It possesses unique physicochemical properties, such as high surface area, porosity, and surface functional groups, which make it an excellent adsorbent for a wide range of pollutants, including synthetic dyes [9, 10].

Additionally, biochar is derived from renewable sources and can be produced using waste biomass, making it an environmentally friendly option for wastewater treatment

¹ Department of Chemistry, The New College Kolhapur, Shivaji University Kolhapur, 416012 India

² Department of Physics, Shri Yashwantrao Patil Science College Solankur, Shivaji University Kolhapur, 416212 India

*Author to whom correspondence should be addressed:

rrahulpatil@gmail.com (R.P.); ashokdchougale@gmail.com (A.C.)

[11]. The utilization of biochar for dye removal offers several advantages. Its high surface area and porosity provide ample sites for dye molecules to adsorb, effectively removing them from wastewater [12].

The production of biochar can be achieved through various methods, such as hydrothermal carbonization, superheated steam torrefaction, and pyrolysis using a pilot carbonization kiln [13, 14]. The production process and the type of feedstock used can significantly influence the biochar's properties and its effectiveness in various applications [15]. For instance, biochar produced from sugarcane bagasse through a pyrolysis or gasification process has been used as catalysts for the biodiesel production process [16]. Additionally, chemical activation of biochar derived from pine needles and coconut shells has been studied to optimize the production process and improve the material's characteristics for specific applications [17].

Several methods have been developed for producing biochar, each with its advantages and limitations. In this section, we provide a brief overview of common methods for producing biochar, including pyrolysis, gasification, and hydrothermal carbonization. We discuss the principles underlying each method, key process parameters, and the characteristics of the resulting biochar products. Understanding the different methods for producing biochar is essential for optimizing its properties and tailoring its application to specific environmental challenges, such as dye pollution in water bodies.

Pyrolysis: This is a thermo-chemical process of biomass conversion to a carbon neutral or better fuels and materials from biomass. It is a thermal decomposition of organic material in a controlled (insufficient) oxygen at a high temperature, thereby producing solid (biochar), liquid (oil), and gaseous products. Biochar produced during this process is a valuable material that can be utilized as a soil additive and in carbon sequestration, where the carbon can be stored (locked) in the soil [18].

Hydrothermal Carbonization (HTC): This is a process that converts wet biomass into biochar and biocrude oil in a high-pressure and high-temperature environment. It is a more efficient method for converting wet biomass into biochar compared to pyrolysis, as it does not require drying of the feedstock [19].

Gasification: This is a process that converts biomass into a gaseous product, which can be used as a fuel, and a solid product, which is biochar. It is a more complex process compared to pyrolysis, as it involves the partial oxidation of biomass in a high-temperature environment [20].

Torrefaction: This is a mild form of pyrolysis that is used to produce biochar from biomass at lower temperatures compared to pyrolysis. It is a more energy-efficient method compared to pyrolysis, as it uses less energy to heat the biomass. The resulting biochar has a higher energy density compared to biochar produced through pyrolysis [21].

2. PROPERTIES OF BIOCHAR RELEVANT TO DYE REMOVAL

The effectiveness of biochar as an adsorbent for dye removal is intricately linked to its unique physicochemical properties. Understanding these properties is essential for optimizing the performance of biochar-based adsorption processes in treating dye-contaminated wastewater. In this section, we explore the key properties of biochar that play a crucial role in its efficacy for dye removal. These properties include surface area, porosity, surface functional groups, surface charge, and structural characteristics (Fig. 1). By elucidating the relationship between biochar properties and dye adsorption behavior, we can enhance our understanding of the mechanisms underlying dye removal processes and design more efficient and sustainable strategies for mitigating dye pollution in water bodies.

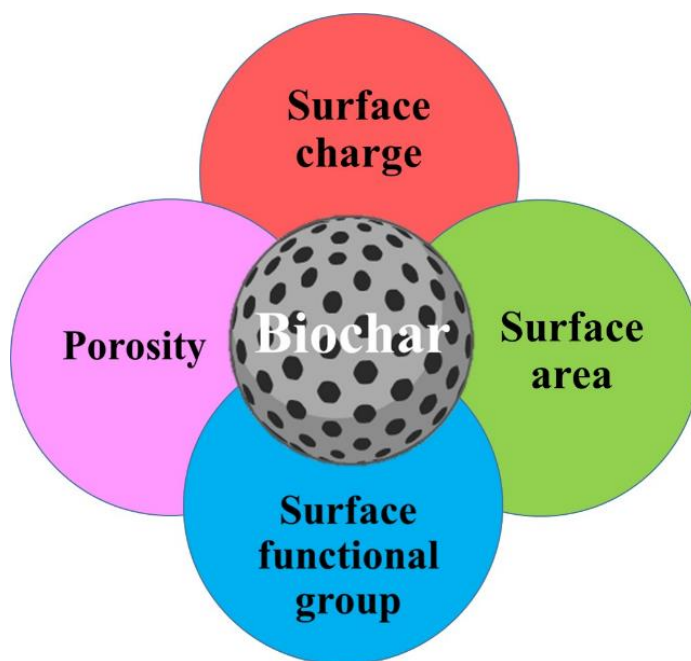


Fig. 1. Properties to improve the biochar efficiency.

Numerous studies have highlighted the direct correlation between biochar surface area and its adsorption capacity for organic dyes. The extensive surface area of biochar provides many active sites and pore structures, facilitating the adsorption of dye molecules from aqueous solutions. Research by Yao et al. [22] demonstrated that biochar with higher surface area exhibited superior adsorption performance for various organic dyes compared to biochar with lower surface area. This finding underscores the significance of surface area in enhancing the adsorption capacity of biochar for dye removal. Similarly, studies by Wang et al. [15] and Zhang et al. [23] validated these findings, showing that biochar with larger surface area effectively removed a wide range of dye pollutants from wastewater. Furthermore, investigations into the effect of surface area on dye removal kinetics have elucidated the role of surface area in governing the rate of adsorption. Sterenzon et al. [24] observed that biochar with higher surface area exhibited faster dye adsorption kinetics, attributed to its increased

accessibility of active sites for dye molecules. This suggests that surface area not only influences the adsorption capacity but also impacts the efficiency and kinetics of dye removal processes. Given the crucial role of surface area in biochar, researchers consistently seek methods to enhance it. Truong et al. [25] employed KHCO_3 as an effective activator to increase the surface area of biochar derived from *Sargassum hemiphyllum*. Their study showed the use of KHCO_3 escalated the surface area of biochar from 976 to $2024 \text{ m}^2\text{g}^{-1}$. The researchers also utilized a method involving low-temperature pyrolysis and high-temperature copyrolysis with potassium hydroxide (KHCO_3) to increase the surface area of the magnetic biochars (NMPBs) [26]. Similarly Liu et al. [27] uses the active reagents to expand the specific surface area to increase the amount of adsorption. Researchers shown that after the modification treatment, the specific surface area of the two altered biochars expanded, both exhibiting a mesoporous distribution (Fig. 2). The pore size generated by WSC was larger, while the specific surface area of WSC was smaller compared to that of WPC. The micropore surface areas and average pore sizes of the NMPBs were higher than those reported for porous carbon derived from copyrolysis with hydroxide and biomass.

Porosity is another important property of biochar that affects its adsorption capacity. Moreover, the mesoporous and microporous structure of high-surface-area biochar has been found to enhance dye adsorption by providing additional adsorption sites and diffusion pathways. Recent studies have demonstrated that biochar with hierarchical pore structures and high surface area showed enhanced dye adsorption performance due to improved accessibility and diffusion of dye molecules into the internal pores [28, 29].

The KOH activated biochar has shown the increased porosity and hence the amount of dye removal [30]. The use of active agents is a trend modify the pore size and hence the surface area (Fig. 3). The nitrogen-doped porous biochar in the study had a micropore volume of $0.14 \text{ cm}^3/\text{g}$, which contributed to its high adsorption capacity of 173.9 mg/g for the Reactive Orange 16 dye [31]. Similarly, the activated biochar pyrolyzed at $750 \text{ }^\circ\text{C}$ had a total pore volume of $0.65 \text{ cm}^3/\text{g}$, which contributed to its high adsorption capacity of 65.9 mg/g for the cationic dye [24].

A comprehensive literature survey reveals the critical importance of surface functional groups in biochar for efficient dye removal in wastewater treatment. Surface functional groups, such as hydroxyl ($-\text{OH}$), carboxyl ($-\text{COOH}$), and phenolic ($-\text{Ph}$) groups, play a significant role in facilitating the adsorption of dye molecules onto the biochar surface. Numerous studies have demonstrated that surface functional groups significantly influence the adsorption capacity and selectivity of biochar for organic dyes. For instance, Hasan et al. [32] and Ghazy et al. [33] found that biochar with a higher abundance of hydroxyl groups exhibited enhanced adsorption performance for cationic dyes due to electrostatic interactions between the hydroxyl groups and the dye molecules. Similarly, biochar modified with carboxyl groups showed improved adsorption efficiency for anionic dyes through electrostatic attraction and π - π interactions [34–36].

Liu and colleagues [37] demonstrated that conventional carbon microspheres (CMS), after amino modification (AF-CMS), exhibited significantly enhanced efficacy in capturing almost 100% of both methyl orange (MO) and tartrazine (TTZ).

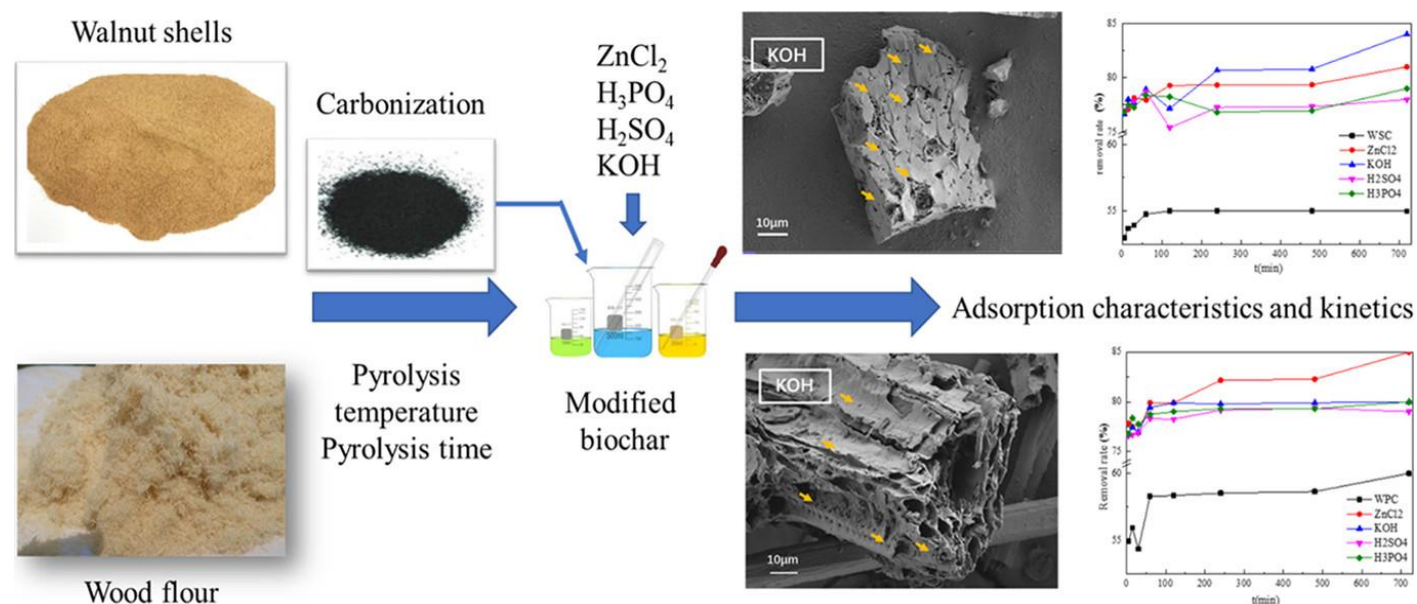


Fig. 2. Biochar synthesis and surface area modification to increase the absorption rate. Reprinted with permission from ref. [27], Liu, C., Wang, W., Wu, R., Liu, Y., Lin, X., Kan, H. and Zheng, Y., 2020. Preparation of acid-and alkali-modified biochar for removal of methylene blue pigment. *ACS omega*, 5(48), pp.30906-30922. Copyright © ACS Publications

This remarkable improvement in performance can be ascribed to the electrostatic attraction between the positively charged amine groups on AF-CMS and the anionic dyes. Furthermore, research by Zhang et al. [38] highlighted the importance of surface functional groups in controlling the surface chemistry and reactivity of biochar for dye adsorption. They found that biochar with a higher density of phenolic groups exhibited superior adsorption capacity for aromatic

dyes, attributed to the formation of π - π interactions between the phenolic groups and the aromatic rings of the dye molecules. Additionally, the surface functional group modifier like KOH and chitosan (CHKBC) exhibited an enriched composition of functional groups such as -COOH, -NH₂, and -OH, leading to a substantial increase in the maximum adsorption of MB by the biochar from 8.83 mg g⁻¹ to 62.04 mg g⁻¹, a 7.03-fold increase [39].

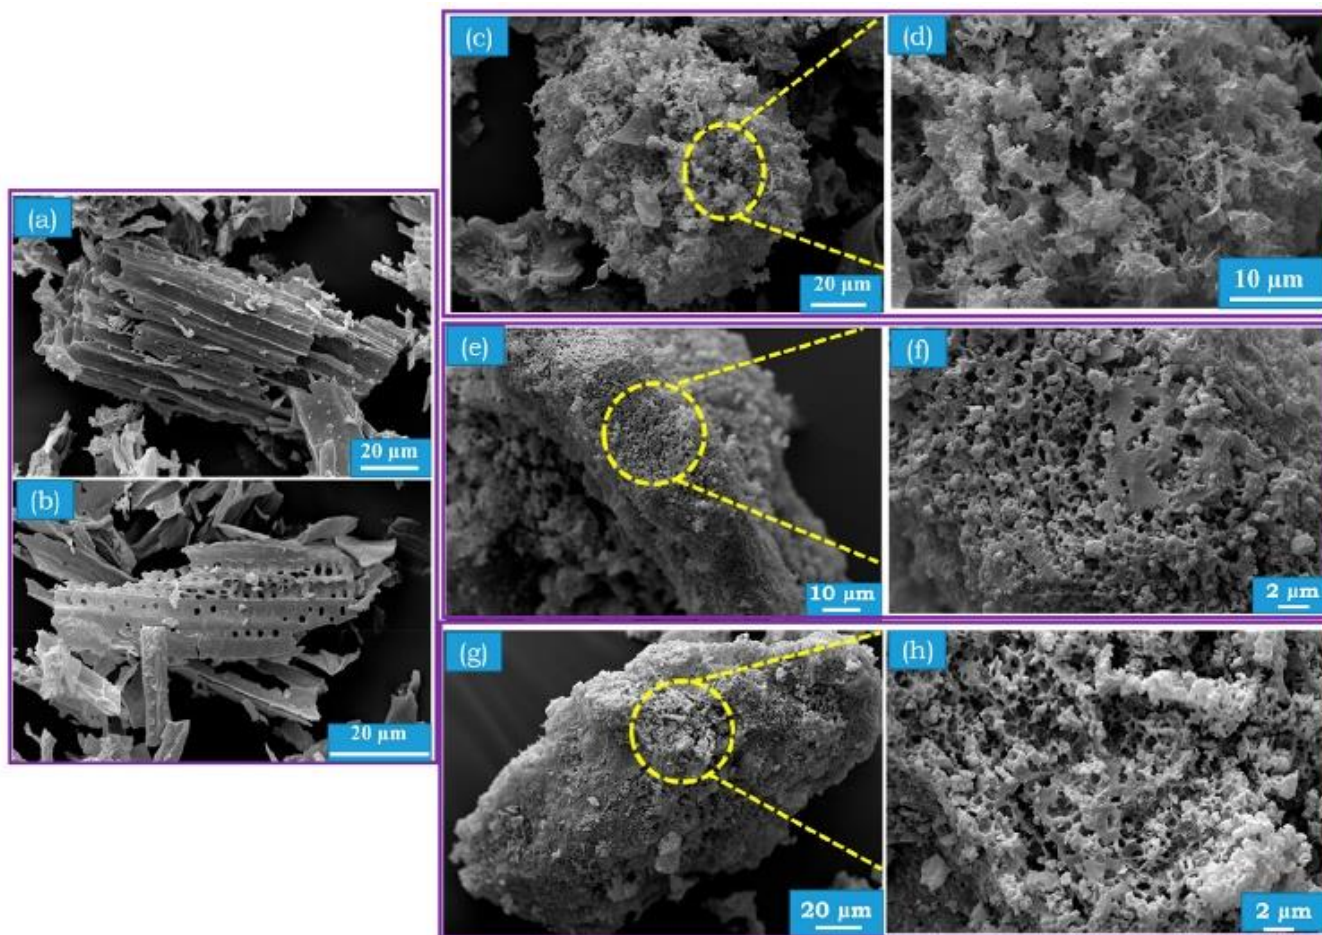


Fig. 3. SEM micrographs of the base biochar without activation (a,b) and with activation (with KOH) (c-h). Reprinted with permission from ref. [30], Priyanka, Vashisht, D., Ibadon, A.O., Mehta, S.K. and Taylor, M.J., 2024. Enhanced Wastewater Remediation Using Mesoporous Activated Wheat Straw Biochars: A Dye Removal Perspective. *ACS Sustainable Resource Management*, 1(2), pp.355-367. Copyright © ACS Publications.

Surface modification of biochar serves not only to augment its dye removal capacity but also to play a vital role in the regeneration and reusability of biochar-based adsorbents. Yang et al. [40] demonstrated that functional groups on the biochar surface can undergo chemical reactions with dye molecules during adsorption, leading to the formation of stable complexes. This enables the desorption of dye molecules from the biochar surface under certain conditions, allowing for the regeneration of the adsorbent and its subsequent reuse in wastewater treatment processes. The functional groups also influence adsorption mechanisms differently for various contaminants, affecting regeneration

differently. For instance, functional groups rich in electrons promote π -interactions and hydrogen bonds during dye adsorption, leading to higher regeneration efficiency [41].

In wastewater treatment processes, biochar serves as an effective agent for removing dyes. This effectiveness stems from the surface charge characteristics of biochar, which are predominantly determined by its functional groups and the pH conditions of the environment. These surface charges enable biochar to engage in electrostatic interactions with dye molecules present in the wastewater. Essentially, biochar acts as a sort of magnet, attracting and binding dye molecules to its surface. The specific functional groups on the biochar's

surface influence the nature of these interactions. For instance, functional groups like carboxyl (-COOH) or hydroxyl (-OH) can impart negative charges to the biochar

surface under certain pH conditions, facilitating attraction to positively charged dye molecules.

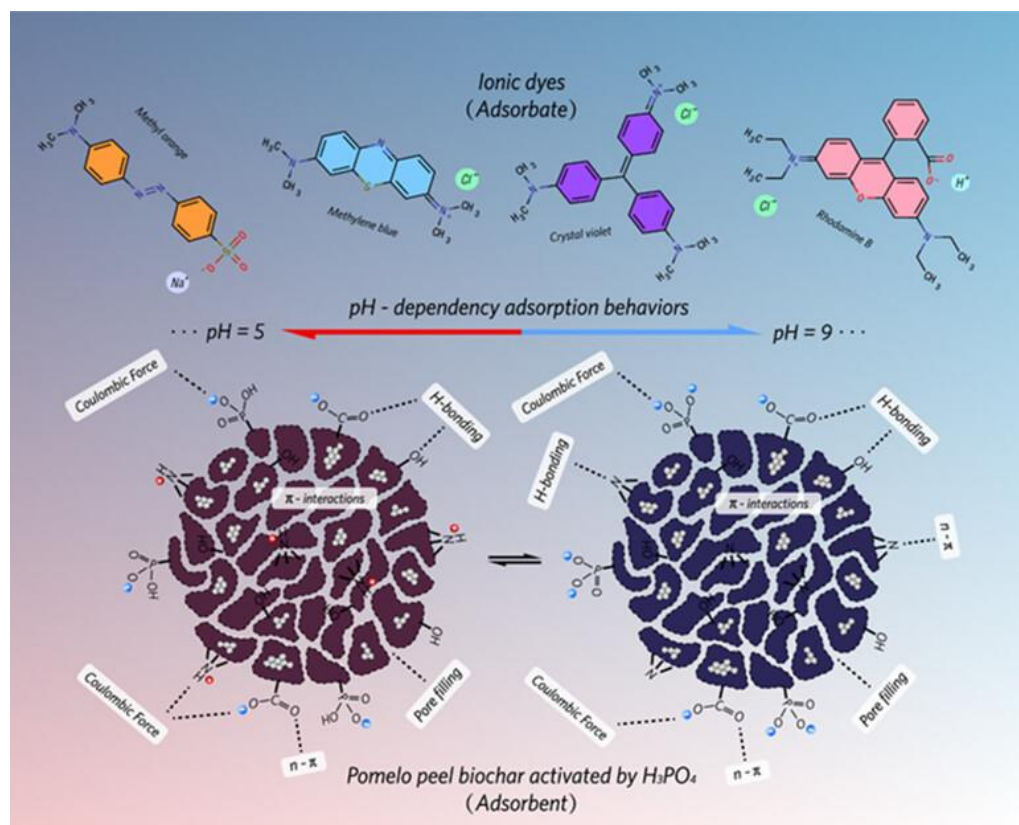


Fig. 4. Effect of pH on the absorption capacity of biochar. Reprinted with permission from ref. [42], Wei, F., Zhu, Y., He, T., Zhu, S., Wang, T., Yao, C., Yu, C., Huang, P., Li, Y., Zhao, Q. and Song, W., 2022. Insights into the pH-dependent adsorption behavior of ionic dyes on phosphoric acid-activated biochar. *ACS omega*, 7(50), pp.46288-46302. Copyright© ACS Publications.

Conversely, in acidic conditions, protonation of these functional groups can result in a positively charged biochar surface, enhancing the adsorption of negatively charged dye molecules through electrostatic attraction. This interplay between the surface charge of biochar and the characteristics of dye molecules ultimately determines the adsorption capacity and efficiency of the process. By understanding and optimizing these factors, wastewater treatment systems can leverage biochar effectively to remove dyes, thereby contributing to cleaner water resources and environmental sustainability.

The surface charge of biochar, primarily influenced by functional groups and pH conditions, plays a crucial role in electrostatic interactions with dye molecules, ultimately affecting adsorption capacity and efficiency [42]. Studies shown that adsorption of ionic dyes with single-polarity charges like methyl orange (MO), methylene blue (MB), and crystal violet (CV), the electrostatic force predominantly determines the pH-dependent character. However, for RhB, factors such as electrostatic force, self-aggregation, and H-bonding collectively contribute to its pH-dependent adsorption behavior, resulting in a synergistic effect (Fig. 4). Likewise, favorable adsorption of cationic dyes such as MB

and CV occurs under alkaline conditions. Conversely, it exhibits enhanced adsorption of anionic dyes like MO under acidic conditions. Several studies have highlighted the impact of surface charge on the adsorption behavior of biochar towards different types of dyes [43]. For example, Xu et al. [44] investigated the adsorption of cationic dyes onto biochar and found that the positively charged surface of biochar facilitated the electrostatic attraction and adsorption of cationic dye molecules. Conversely, the adsorption of anionic dyes and observed that biochar with a negatively charged surface exhibited enhanced adsorption capacity for anionic dye molecules through electrostatic interactions [45]. Similarly, Ullah et al. [41] demonstrated the surface charge of adsorbent materials plays a crucial role in the adsorption process. The activated biochar (ABC600) had a pH_{Hzc} value of 3.0, suggesting it may have a negative charge above this pH and a positive charge below it. Thus, at pH values higher than pH_{Hzc}, cationic dye adsorption is favored, while at pH values lower than pH_{Hzc}, anionic dye adsorption is more likely to occur. The study emphasized the significance of pH-dependent surface charge in regulating the adsorption behavior of biochar. The nitrogen-doped porous biochar in the study had a positive surface charge at pH 2.0, which

contributed to its high adsorption capacity of 173.9 mg/g for the Reactive Orange 16 dye [46]. Similarly, the activated biochar pyrolyzed at 750 °C had a positive surface charge at pH 2.0, which contributed to its high adsorption capacity of 65.9 mg/g for the cationic dye [47].

3. RECENT ADVANCES IN BIOCHAR-BASED DYE REMOVAL

Recent studies have focused on optimizing the adsorption processes of biochar for efficient dye removal [48, 49]. Modification of biochar properties, synthesis of composite materials, and optimization of adsorption processes are crucial aspects in enhancing the efficiency and applicability of biochar-based adsorbents for pollutant removal from various environmental matrices. Several studies have explored enhancing biochar properties through innovative methods. For instance, the research on milkvetch-derived biochar involved decorating it with ZnO-Ce nanoparticles, leading to enhanced photocatalytic performance for reactive blue 19 dye removal [50]. This modification strategy demonstrates a novel approach to improving biochar's effectiveness in dye removal processes.

Likewise, the simple chemical modification is also popular for the biochar modifications. This mainly includes acid modification, alkaline modification, oxidation agent modification, and modification with metal salts. Acid modification aims to eliminate impurities like metals and add acid functional groups to biochar surfaces using acids like hydrochloric, sulfuric, nitric, phosphoric, oxalic, and citric acid [49, 51]. Alkaline modification seeks to boost surface area and oxygen-containing functional groups using agents like potassium hydroxide and sodium hydroxide [52, 53]. Furthermore, for oxidative biochar modification, potassium permanganate and hydrogen peroxide are commonly used oxidizing agents. These agents play a crucial role in introducing functional groups onto the biochar surface, thereby altering its physicochemical properties [54–56].

The modification of biochar using metal salts or metal oxides can certainly alter its characteristics significantly. By incorporating metals or metal oxides into biochar, the sorption capacity for heavy metals can be enhanced, leading to improved adsorption, catalytic performance, and magnetic properties [57–59]. This modification process involves mixing the metals or metal oxides with raw materials before pyrolysis or soaking biochar in metal solutions under specific conditions, resulting in changes in physicochemical properties and functional groups on the biochar surface [57–59]. The presence of metal oxides in biochar can enhance its sorption capacity for pollutants, facilitate their removal from water and sewage, and improve interactions such as electrostatic attraction and surface complexation, making biochar an effective material for wastewater treatment technologies [58].

Apart from the abovementioned methods of modification, biochar materials were also employed to enhance the surface area of biochar. Additionally, biochar modification using organic solvents has been documented.

Methanol, for instance, facilitates esterification between carbonyl groups and municipal solid waste-derived biochar, resulting in a notable increase in adsorption capacity for compounds like tetracycline [60]. Ammonia gas modification introduces nitrogen-containing groups onto the biochar surface, as demonstrated by Xiong et al. [61]. Moreover, steam and gas purging modifications involve two distinct processes: first, the pyrolysis of the feedstock, followed by the modification of biochar through the purging of carbon dioxide or ammonia gas [62].

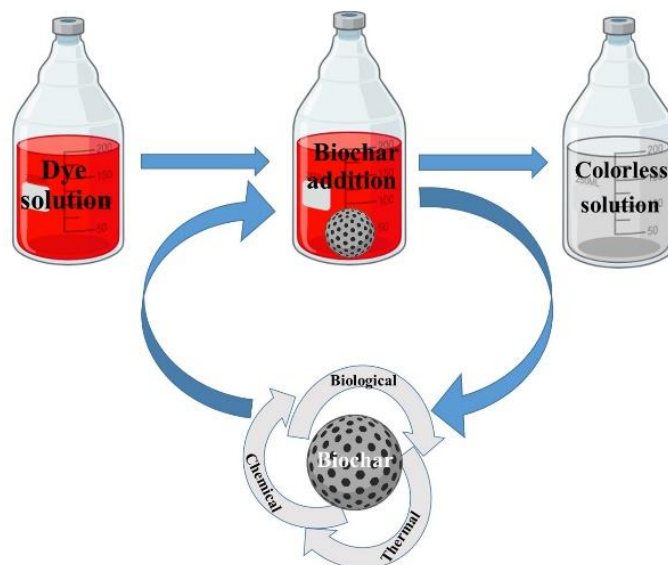


Fig. 5. Recovery and reuse of the biochar of effective use.

4. CHALLENGES AND FUTURE PERSPECTIVES

The challenges and future perspectives of biochar as a biosorbent for water remediation are multifaceted. The effectiveness of biosorption processes heavily relies on the choice of biosorbent, which in turn is influenced by various factors. Researchers emphasize the importance of selecting biosorbents that are abundant and freely available in nature, encouraging the exploration of biochar as a promising option due to its availability [63]. Despite its potential as a cost-effective and environmentally friendly alternative for pollutant removal, some researchers have questioned its commercial viability due to complexities in physicochemical and biological factors involved in pollutant removal. Consequently, there is a growing emphasis on enhancing biosorption capacity, selectivity, kinetics, and the possibility of regeneration or re-use of biosorbents.

The significant challenge facing the practical application of biochar for dye removal is the regeneration of spent biochar, which is critical for sustainable and cost-effective operations [64,65]. Additionally, the scalability of biochar-based dye removal processes presents a hurdle, requiring efficient and large-scale production methods to meet industrial demands [66]. Moreover, the cost-effectiveness of biochar production and utilization impacts its

economic viability for dye removal on a larger scale [50].

Future research should prioritize the development of effective regeneration techniques for spent biochar to enhance its reusability and sustainability in dye removal processes [67, 68]. Regeneration techniques for spent biosorbents play a crucial role in reducing production costs and energy consumption, contributing to sustainable waste management practices. Addressing scalability issues necessitates research into optimizing biochar production methods and scaling up manufacturing processes to meet industrial needs [50, 69]. Exploring innovative and cost-effective approaches for biochar production and application can overcome economic barriers, making biochar-based dye removal more commercially viable [69]. Various techniques for recovering and regenerating spent adsorbents, such as magnetic separation, filtration, thermal desorption, chemical desorption, supercritical fluid desorption, advanced oxidation processes, and microbial-assisted regeneration, are discussed [70] (Fig. 5). Furthermore, research into advanced biochar materials, composites, or nanocomposites can enhance the efficiency and effectiveness of biochar in dye removal processes, improving overall performance and sustainability. Modification techniques, such as ionizing radiation, offer environmentally friendly alternatives to chemical modification, enhancing fibre compatibility without compromising original features. Moreover, continuous market research is essential to understand industrial requirements and drive innovation in biochar-based dye removal. By addressing these challenges and focusing on future research directions, the practical application of biochar for dye removal can be optimized, leading to more sustainable, efficient, and cost-effective solutions in water treatment and environmental remediation.

5. CONCLUSIONS

In conclusion, the review highlights the urgent need for sustainable and efficient methods to address dye pollution in water bodies, which poses significant threats to aquatic ecosystems and human health. Biochar has emerged as a promising solution due to its unique physicochemical properties and environmental advantages. The review explores the key properties of biochar relevant to dye removal, emphasizing the importance of surface area, porosity, surface functional groups, surface charge, and structural characteristics in enhancing its adsorption capacity. Recent advances in biochar-based dye removal, including modification techniques and synthesis of composite materials, have shown promising results in improving the efficiency and applicability of biochar-based adsorbents. However, several challenges need to be addressed to realize the full potential of biochar in water remediation, including regeneration of spent biochar, scalability issues, and economic viability. Future research should focus on developing effective regeneration techniques, optimizing production methods, exploring innovative approaches for biochar synthesis, and advancing biochar materials to overcome these challenges and pave the

way for more sustainable, efficient, and cost-effective solutions in dye removal and environmental remediation.

CONFLICT OF INTEREST

The authors declare that there is no conflict of interests.

REFERENCES

- [1] Pandi, A., Kuppaswami, G.M., Ramudu, K.N. and Palanivel, S., 2019. A sustainable approach for degradation of leather dyes by a new fungal laccase. *Journal of Cleaner Production*, 211, pp.590-597.
- [2] Tudoran, C., Roşu, M.C. and Coroş, M., 2020. A concise overview on plasma treatment for application on textile and leather materials. *Plasma Processes and Polymers*, 17(8), p.2000046.
- [3] Islam, T., Repon, M.R., Islam, T., Sarwar, Z. and Rahman, M.M., 2023. Impact of textile dyes on health and ecosystem: A review of structure, causes, and potential solutions. *Environmental Science and Pollution Research*, 30(4), pp.9207-9242.
- [4] Dutta, S., Adhikary, S., Bhattacharya, S., Roy, D., Chatterjee, S., Chakraborty, A., Banerjee, D., Ganguly, A., Nanda, S. and Rajak, P., 2024. Contamination of textile dyes in aquatic environment: Adverse impacts on aquatic ecosystem and human health, and its management using bioremediation. *Journal of Environmental Management*, 353, p.120103.
- [5] Chavan, R., Mujawar, S., Dawkar, V., More, V., Pawar, N., Patil, R., Jadhav, J., Mustafa, J., Jameel, B., Muhaisen, H.M. and Mohammed, A.Y., 2024. Enhanced Photodegradation of Methylene Blue Using Reusable Cobalt Ferrite Nanocomposites. *Science of Advanced Materials*, 16(5), pp.589-595.
- [6] Chavan, R., Bhat, N., Parit, S., Narasimharao, K., Devan, R.S., Patil, R.B., Karade, V.C., Pawar, N.V., Kim, J.H., Jadhav, J.P. and Chougale, A.D., 2023. Development of magnetically recyclable nanocatalyst for enhanced Fenton and photo-Fenton degradation of MB and Cr (VI) photo-reduction. *Materials Chemistry and Physics*, 293, p.126964.
- [7] Al-Gethami, W., Qamar, M.A., Shariq, M., Alaghaz, A.N.M., Farhan, A., Areshi, A.A. and Alnasir, M.H., 2024. Emerging environmentally friendly bio-based nanocomposites for the efficient removal of dyes and micropollutants from wastewater by adsorption: a comprehensive review. *RSC Advances*, 14(4), pp.2804-2834.
- [8] Srinivasan, G.R., 2023. Experimental Study of Biochar Production Process Using a Pilot Carbonization Kiln as a Biofuel's Properties Improvement Module. *Asian Journal of Environment & Ecology*, 22(3), pp.133-140.
- [9] Lin, X., Zhou, Q., Xu, H., Chen, H. and Xue, G., 2023. Advances from conventional to biochar enhanced biotreatment of dyeing wastewater: A critical review. *Science of The Total Environment*, p.167975.

- [10] Yan, C., Li, J., Sun, Z., Wang, X. and Xia, S., **2024**. Mechanistic insights into removal of pollutants in adsorption and advanced oxidation processes by livestock manure derived biochar: A review. *Separation and Purification Technology*, p.127457.
- [11] Nguyen, T.H., Paramasivam, P., Le, H.C. and Nguyen, D.C., **2024**. Harnessing a Better Future: Exploring AI and ML Applications in Renewable Energy. *JOIV: International Journal on Informatics Visualization*, 8(1), pp.55-78.
- [12] Yaashikaa, P.R., Karishma, S., Kamalesh, R., Saravanan, A., Vickram, A.S. and Anbarasu, K., **2024**. A systematic review on enhancement strategies in biochar-based remediation of polycyclic aromatic hydrocarbons. *Chemosphere*, p.141796.
- [13] Is'emin, R.L., Kuz'min, S.N., Konyakhin, V.V., Milovanov, O.Y., Mikhalev, A.V., Muratova, N.S., Nebyvaev, A.V. and Kokh-Tatarenko, V.S., **2022**. Comparative studies of the biochar production process using hydrothermal carbonization and superheated steam torrefaction. *Thermal Engineering*, 69(12), pp.981-988.
- [14] Chen, W.H., Lin, B.J., Lin, Y.Y., Chu, Y.S., Ubando, A.T., Show, P.L., Ong, H.C., Chang, J.S., Ho, S.H., Culaba, A.B. and Pétrissans, A., **2021**. Progress in biomass torrefaction: Principles, applications and challenges. *Progress in Energy and Combustion Science*, 82, p.100887.
- [15] Wang, H., Gao, B., Fang, J., Ok, Y.S., Xue, Y., Yang, K. and Cao, X., **2018**. Engineered biochar derived from eggshell-treated biomass for removal of aqueous lead. *Ecological Engineering*, 121, pp.124-129.
- [16] e Melo, V.M., Ferreira, G.F. and Fregolente, L.V., **2024**. Sustainable catalysts for biodiesel production: The potential of CaO supported on sugarcane bagasse biochar. *Renewable and Sustainable Energy Reviews*, 189, p.114042.
- [17] Azad, D., Pateriya, R.N. and Sharma, R.K., **2024**. Chemical activation of pine needle and coconut shell biochar: production, characterization and process optimization. *International Journal of Environmental Science and Technology*, 21(1), pp.757-772.
- [18] Foong, S.Y., Liew, R.K., Yek, P.N.Y., Chan, Y.H. and Lam, S.S., **2024**. A Review in Production of Nitrogen-Enriched Carbon Materials via Chitin Pyrolysis and Activation for Enhanced Wastewater Remediation. *Current Opinion in Green and Sustainable Chemistry*, p.100920.
- [19] Supee, A.H. and Zaini, M.A.A., **2024**. Hydrothermal carbonization of biomass: a commentary. *Fullerenes, Nanotubes and Carbon Nanostructures*, 32(2), pp.119-127.
- [20] Enaime, G., Baçaoui, A., Yaacoubi, A. and Lübken, M., **2020**. Biochar for wastewater treatment—conversion technologies and applications. *Applied Sciences*, 10(10), p.3492.
- [21] Yang, X., Zhao, Z., Zhao, Y., Xu, L., Feng, S., Wang, Z., Zhang, L. and Shen, B., **2024**. Effects of torrefaction pretreatment on fuel quality and combustion characteristics of biomass: A review. *Fuel*, 358, p.130314.
- [22] Yao, Q., Liu, J., Yu, Z., Li, Y., Jin, J., Liu, X. and Wang, G., **2017**. Three years of biochar amendment alters soil physiochemical properties and fungal community composition in a black soil of northeast China. *Soil Biology and Biochemistry*, 110, pp.56-67.
- [23] Zhang, E., Wang, L., Zhang, B., Xie, Y. and Wang, G., **2019**. Shape-controlled hydrothermal synthesis of CuFe₂O₄ nanocrystals for enhancing photocatalytic and photoelectrochemical performance. *Materials Chemistry and Physics*, 235, p.121633.
- [24] Jellali, S., Azzaz, A.A., Al-Harrasi, M., Charabi, Y., Al-Sabahi, J.N., Al-Raeesi, A., Usman, M., Al Nasiri, N., Al-Abri, M. and Jeguirim, M., **2022**. Conversion of industrial sludge into activated biochar for effective cationic dye removal: Characterization and adsorption properties assessment. *Water*, 14(14), p.2206.
- [25] Truong, Q.M., Nguyen, T.B., Chen, C.W., Chen, W.H., Bui, X.T. and Dong, C.D., **2024**. KHCO₃-activated high surface area biochar derived from brown algae: A case study for efficient adsorption of Cr (VI) in aqueous solution. *Environmental Research*, 247, p.118227.
- [26] Chen, L., Wang, M., Sun, Q., Zhao, Z., Han, J., Ji, R., Jiang, X., Song, Y., Xue, J. and Cheng, H., **2024**. A three-step process to produce biochar with good magnetism, high specific surface area, and high levels of nitrogen doping for the efficient removal of sulfamethoxazole. *Separation and Purification Technology*, 333, p.125940.
- [27] Liu, C., Wang, W., Wu, R., Liu, Y., Lin, X., Kan, H. and Zheng, Y., **2020**. Preparation of acid-and alkali-modified biochar for removal of methylene blue pigment. *ACS Omega*, 5(48), pp.30906-30922.
- [28] Wang, C., Lin, X., Zhang, X. and Show, P.L., **2024**. Research advances on production and application of algal biochar in environmental remediation. *Environmental Pollution*, p.123860.
- [29] Guo, H., Liu, Y., Lv, Y., Liu, Y., Lin, Y. and Liu, M., **2024**. Nitrogen doped sinocalamus oldhami lignin-based activated biochar with high specific surface area: Preparation and its adsorption for malachite green contaminant. *Process Safety and Environmental Protection*, 183, pp.992-1001.
- [30] Priyanka, Vashisht, D., Ibhaddon, A.O., Mehta, S.K. and Taylor, M.J., **2024**. Enhanced Wastewater Remediation Using Mesoporous Activated Wheat Straw Biochars: A Dye Removal Perspective. *ACS Sustainable Resource Management*, 1(2), pp.355-367.
- [31] Ekman, S., Dos Reis, G.S., Laisné, E., Thivet, J., Grimm, A., Lima, E.C., Naushad, M. and Dotto, G.L., **2023**. Synthesis, characterization, and adsorption properties of nitrogen-doped nanoporous biochar: efficient removal of reactive Orange 16 Dye and colorful effluents. *Nanomaterials*, 13(14), p.2045.
- [32] Hasan, M.M., Shenashen, M.A., Hasan, M.N., Znad, H., Salman, M.S. and Awual, M.R., **2021**. Natural

- biodegradable polymeric bioadsorbents for efficient cationic dye encapsulation from wastewater. *Journal of Molecular Liquids*, 323, p.114587.
- [33] Ghazy, N.M., Ghaith, E.A., Abou El-Reash, Y.G., Zaky, R.R., Abou El-Maaty, W.M. and Awad, F.S., **2022**. Enhanced performance of hydroxyl and cyano group functionalized graphitic carbon nitride for efficient removal of crystal violet and methylene blue from wastewater. *RSC Advances*, 12(55), pp.35587-35597.
- [34] Sutradhar, S., Mondal, A., Kuehne, F., Krueger, O., Rakshit, S.K. and Kang, K., **2024**. Comparison of Oil-Seed Shell Biomass-Based Biochar for the Removal of Anionic Dyes—Characterization and Adsorption Efficiency Studies. *Plants*, 13(6), p.820.
- [35] Dong, X., Chu, Y., Tong, Z., Sun, M., Meng, D., Yi, X., Gao, T., Wang, M. and Duan, J., **2024**. Mechanisms of adsorption and functionalization of biochar for pesticides: A review. *Ecotoxicology and Environmental Safety*, 272, p.116019.
- [36] Aichour, A., Zaghouane-Boudiaf, H. and Khodja, H.D., **2022**. Highly removal of anionic dye from aqueous medium using a promising biochar derived from date palm petioles: Characterization, adsorption properties and reuse studies. *Arabian Journal of Chemistry*, 15(1), p.103542.
- [37] Liu, M., Zheng, J., Wang, L., Hu, Z., Lan, S., Rao, W., Liu, Y., Xie, Y. and Yu, C., **2022**. Ultrafast and selective adsorption of anionic dyes with amine-functionalized glucose-based adsorbents. *Journal of Molecular Structure*, 1263, p.133150.
- [38] Zhang, Y., Xu, X., Cao, L., Ok, Y.S. and Cao, X., **2018**. Characterization and quantification of electron donating capacity and its structure dependence in biochar derived from three waste biomasses. *Chemosphere*, 211, pp.1073-1081.
- [39] Su, X., Wang, X., Ge, Z., Bao, Z., Lin, L., Chen, Y., Dai, W., Sun, Y., Yuan, H., Yang, W. and Meng, J., **2024**. Koh-activated biochar and chitosan composites for efficient adsorption of industrial dye pollutants. *Chemical Engineering Journal*, 486, p.150387.
- [40] Yang, Y., Nguyen, T.M.P., Van, H.T., Nguyen, Q.T., Nguyen, T.H., Nguyen, T.B.L., Van Thanh, D., Nguyen, T.V., Thang, P.Q. and Yilmaz, M., **2022**. ZnO nanoparticles loaded rice husk biochar as an effective adsorbent for removing reactive red 24 from aqueous solution. *Materials Science in Semiconductor Processing*, 150, p.106960.
- [41] Alsawy, T., Rashad, E., El-Qelish, M. and Mohammed, R.H., **2022**. A comprehensive review on the chemical regeneration of biochar adsorbent for sustainable wastewater treatment. *NPJ Clean Water*, 5(1), p.29.
- [42] Wei, F., Zhu, Y., He, T., Zhu, S., Wang, T., Yao, C., Yu, C., Huang, P., Li, Y., Zhao, Q. and Song, W., **2022**. Insights into the pH-dependent adsorption behavior of ionic dyes on phosphoric acid-activated biochar. *ACS Omega*, 7(50), pp.46288-46302.
- [43] Tan, X.F., Zhu, S.S., Wang, R.P., Chen, Y.D., Show, P.L., Zhang, F.F. and Ho, S.H., **2021**. Role of biochar surface characteristics in the adsorption of aromatic compounds: Pore structure and functional groups. *Chinese Chemical Letters*, 32(10), pp.2939-2946.
- [44] Xu, R.K., Xiao, S.C., Yuan, J.H. and Zhao, A.Z., **2011**. Adsorption of methyl violet from aqueous solutions by the biochars derived from crop residues. *Bioresource technology*, 102(22), pp.10293-10298.
- [45] Lian, F. and Xing, B., **2017**. Black carbon (biochar) in water/soil environments: molecular structure, sorption, stability, and potential risk. *Environmental Science & Technology*, 51(23), pp.13517-13532.
- [46] Ekman, S., Dos Reis, G.S., Laisné, E., Thivet, J., Grimm, A., Lima, E.C., Naushad, M. and Dotto, G.L., **2023**. Synthesis, characterization, and adsorption properties of nitrogen-doped nanoporous biochar: efficient removal of reactive Orange 16 Dye and colorful effluents. *Nanomaterials*, 13(14), p.2045.
- [47] Jellali, S., Azzaz, A.A., Al-Harrasi, M., Charabi, Y., Al-Sabahi, J.N., Al-Raeesi, A., Usman, M., Al Nasiri, N., Al-Abri, M. and Jeguirim, M., **2022**. Conversion of industrial sludge into activated biochar for effective cationic dye removal: Characterization and adsorption properties assessment. *Water*, 14(14), p.2206.
- [48] Sizmur, T., Fresno, T., Akgül, G., Frost, H. and Moreno-Jiménez, E., **2017**. Biochar modification to enhance sorption of inorganics from water. *Bioresource Technology*, 246, pp.34-47.
- [49] Wang, J. and Wang, S., **2019**. Preparation, modification and environmental application of biochar: A review. *Journal of Cleaner Production*, 227, pp.1002-1022.
- [50] Jahani, F., Maleki, B., Mansouri, M., Noorimotlagh, Z. and Mirzaee, S.A., **2023**. Enhanced photocatalytic performance of milkvetch-derived biochar via ZnO-Ce nanoparticle decoration for reactive blue 19 dye removal. *Scientific Reports*, 13(1), p.17824.
- [51] Rajapaksha, A.U., Chen, S.S., Tsang, D.C., Zhang, M., Vithanage, M., Mandal, S., Gao, B., Bolan, N.S. and Ok, Y.S., **2016**. Engineered/designer biochar for contaminant removal/immobilization from soil and water: potential and implication of biochar modification. *Chemosphere*, 148, pp.276-291.
- [52] Fan, Y., Wang, B., Yuan, S., Wu, X., Chen, J. and Wang, L., **2010**. Adsorptive removal of chloramphenicol from wastewater by NaOH modified bamboo charcoal. *Bioresource Technology*, 101(19), pp.7661-7664.
- [53] Jin, H., Capareda, S., Chang, Z., Gao, J., Xu, Y. and Zhang, J., **2014**. Biochar pyrolytically produced from municipal solid wastes for aqueous As (V) removal: adsorption property and its improvement with KOH activation. *Bioresource Technology*, 169, pp.622-629.
- [54] Wang, H., Zhang, Z., Sun, R., Lin, H., Gong, L., Fang, M. and Hu, W.H., **2015**. HPV infection and anemia status stratify the survival of early T2 laryngeal squamous cell carcinoma. *Journal of Voice*, 29(3), pp.356-362.

- [55] Huff, M.D. and Lee, J.W., **2016**. Biochar-surface oxygenation with hydrogen peroxide. *Journal of Environmental Management*, *165*, pp.17-21.
- [56] Xue, Y., Gao, B., Yao, Y., Inyang, M., Zhang, M., Zimmerman, A.R. and Ro, K.S., **2012**. Hydrogen peroxide modification enhances the ability of biochar (hydrochar) produced from hydrothermal carbonization of peanut hull to remove aqueous heavy metals: Batch and column tests. *Chemical Engineering Journal*, *200*, pp.673-680.
- [57] Nguyen, D.L.T., Binh, Q.A., Nguyen, X.C., Nguyen, T.T.H., Vo, Q.N., Nguyen, T.D., Tran, T.C.P., Nguyen, T.A.H., Kim, S.Y., Nguyen, T.P. and Bae, J., **2021**. Metal salt-modified biochars derived from agro-waste for effective congo red dye removal. *Environmental Research*, *200*, p.111492.
- [58] Weidner, E., Karbassiyazdi, E., Altaee, A., Jesionowski, T. and Ciesielczyk, F., **2022**. Hybrid metal oxide/biochar materials for wastewater treatment technology: a review. *ACS Omega*, *7*(31), pp.27062-27078.
- [59] Ahuja, R., Kalia, A., Sikka, R. and P, C., **2022**. Nano modifications of biochar to enhance heavy metal adsorption from wastewaters: a review. *ACS omega*, *7*(50), pp.45825-45836.
- [60] Jing, X.R., Wang, Y.Y., Liu, W.J., Wang, Y.K. and Jiang, H., **2014**. Enhanced adsorption performance of tetracycline in aqueous solutions by methanol-modified biochar. *Chemical Engineering Journal*, *248*, pp.168-174.
- [61] Xiong, Z., Shihong, Z., Haiping, Y., Tao, S., Yingquan, C. and Hanping, C., **2013**. Influence of NH₃/CO₂ modification on the characteristic of biochar and the CO₂ capture. *BioEnergy Research*, *6*, pp.1147-1153.
- [62] Zhang, J., Lü, F., Shao, L. and He, P., **2014**. The use of biochar-amended composting to improve the humification and degradation of sewage sludge. *Bioresource Technology*, *168*, pp.252-258.
- [63] Park, D., Yun, Y.S. and Park, J.M., **2010**. The past, present, and future trends of biosorption. *Biotechnology and Bioprocess Engineering*, *15*, pp.86-102.
- [64] Sinha, R., Kumar, R., Sharma, P., Kant, N., Shang, J. and Aminabhavi, T.M., **2022**. Removal of hexavalent chromium via biochar-based adsorbents: State-of-the-art, challenges, and future perspectives. *Journal of Environmental Management*, *317*, p.115356.
- [65] Singh, M., Ahsan, M., Pandey, V., Singh, A., Mishra, D., Tiwari, N., Singh, P., Karak, T. and Khare, P., **2022**. Comparative assessment for removal of anionic dye from water by different waste-derived biochar vis a vis reusability of generated sludge. *Biochar*, *4*(1), p.13.
- [66] Perveen, S., Nadeem, R., Nosheen, F., Asjad, M.I., Awrejcewicz, J. and Anwar, T., **2022**. Biochar-mediated zirconium ferrite nanocomposites for tartrazine dye removal from textile wastewater. *Nanomaterials*, *12*(16), p.2828.
- [67] Tsoutsas, E.K., Tolkou, A.K., Kyzas, G.Z. and Katsoyiannis, I.A., **2024**. An Update on Agricultural Wastes Used as Natural Adsorbents or Coagulants in Single or Combined Systems for the Removal of Dyes from Wastewater. *Water, Air, & Soil Pollution*, *235*(3), pp.1-21.
- [68] Jaspal, D., **2024**. Dyes and heavy metals: removal, recovery and wastewater reuse—a review. *Sustainable Water Resources Management*, *10*(2), pp.1-14.
- [69] Perveen, S., Nadeem, R., Nosheen, F., Asjad, M.I., Awrejcewicz, J. and Anwar, T., **2022**. Biochar-mediated zirconium ferrite nanocomposites for tartrazine dye removal from textile wastewater. *Nanomaterials*, *12*(16), p.2828.
- [70] Baskar, A.V., Bolan, N., Hoang, S.A., Sooriyakumar, P., Kumar, M., Singh, L., Jasemizad, T., Padhye, L.P., Singh, G., Vinu, A. and Sarkar, B., **2022**. Recovery, regeneration and sustainable management of spent adsorbents from wastewater treatment streams: A review. *Science of the Total Environment*, *822*, p.153555.

AUTHORS INFORMATION



Rupali Chavan is a dedicated Ph.D. student at the Department of Chemistry, The New College, Shivaji University, Kolhapur, specializing in the development of nanomaterials for wastewater treatment. Her current research interest include the green synthesis of nanomaterials, nanocomposites, and characterization of advanced nanomaterials for their catalytic application. She holds a Master's degree in Biochemistry and a Bachelor's degree in Chemistry. Rupali is passionate about using nanotechnology to address global water pollution challenges and is committed to advancing sustainable water treatment solutions through her innovative research. Through her work, Rupali hopes to impact environmental sustainability and public health significantly.



Dr. Rahul Patil earned his MS (2003) and PhD (2008) in Physics from Shivaji University Kolhapur, India. His research focused on oxide thin films using vacuum techniques for thin film optical coatings, investigating their structural, optical, and mechanical properties. He also explored synthesis methods like spin coating, chemical vapor deposition, and spray techniques for polymer and oxide thin films in optical coatings.

In 2009, he joined National Central University Taiwan for Postdoctoral research, concentrating on supported bimetallic nanoclusters for catalytic applications. His work involved fabricating Au–Pt bimetallic nanoclusters on ultra-thin Al_2O_3 films grown on NiAl(100) substrates under ultra-high vacuum conditions. This catalytic system aimed to enhance catalyst performance in methanol fuel cells, demonstrating superior catalytic properties toward methanol oxidation.

Since 2014, he has served as Head of the Physics department at Shri Yashwantrao Patil Science College Solankur, Shivaji University Kolhapur, India. His research interests encompass various areas, including green synthesis of silver nanoparticles, development of magnetically recyclable nanocatalysts, Fenton and photoFenton degradation of organic dyes, heavy metal reduction, oxide thin films and nanoparticles for supercapacitor applications, and magnetic nanoparticles for environmental applications such as wastewater treatment and heavy metal reduction, bifunctional electrodes for electrochemical water splitting. In summary, his research focuses on energy and environmental applications. He has authored several books, tens of research articles in reputable journals, organized six international conferences, served as a guest editor for numerous special issues in prestigious journals, and contributed to many conference proceedings.



Dr. Ashok Dattatraya Chougale, is an esteemed academician and researcher specializing in biochemistry. Currently, he serves as an Assistant Professor in the Department of Chemistry at The New College, Kolhapur. Dr. Chougale's academic journey began at Shivaji University, Kolhapur, where he earned his Bachelor's degree in Chemistry in 2001, followed by a Master's degree in Biochemistry in 2004. He completed his Ph.D. in Biochemistry at the same university in 2008. His doctoral research focused on innovative approaches to treating diabetes using plant-based compounds with hypoglycemic properties.

Currently, Dr. Chougale is actively involved in two significant research projects funded by SERB Delhi (DST) and SUK (Kolhapur), focusing on the development of advanced biosensors for the detection of breast cancer markers and the bioprospecting of natural compounds for diabetes treatment, respectively. These projects underscore his commitment to addressing pressing health challenges through innovative interdisciplinary approaches.

Dr. Chougale's prolific research output is evidenced by his extensive publication record comprising impactful articles in esteemed peer-reviewed journals. His research interests encompass a wide range of topics including nano-biotechnology, enzymology, nanomaterials, catalysis, and drug delivery systems. Notably, Dr. Chougale has contributed significantly to the development of electrochemical immunosensors, magnetic nanoparticles, and green synthesis methods for nanoparticles, offering novel solutions with potential applications in healthcare and environmental remediation.

Despite his demanding academic and research responsibilities, Dr. Chougale remains deeply engaged in scholarly activities, contributing to books, reports, and chapters on biosensors, genetically engineered crops, and lignin properties. His dedication to advancing scientific knowledge extends beyond the laboratory, actively participating in conferences, workshops, and collaborative initiatives aimed at fostering scientific exchange and innovation.